


Product Information

ROHACELL® EC/EC-HT

A VERY SPECIAL FOAM

ROHACELL® EC/EC-HT is a polymethacrylimide (PMI) based foam core material specifically designed for stealth applications.

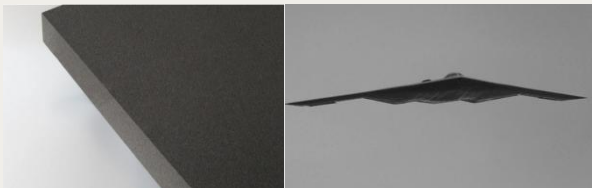

During processing, the polymer is loaded with carbon particles resulting in a conductive foam product that possesses superior dielectric properties and enables absorption of electromagnetic waves at radar frequencies.

DIELECTRIC PROPERTIES

Property	Frequency [GHz]	ROHACELL® 71 EC	ROHACELL® 150 EC
Real part of permittivity	5	1.44	1.83
	10	1.33	1.62
	20	1.25	1.68
	30	1.28	1.52
Imaginary part of permittivity	5	0.18	0.41
	10	0.12	0.30
	20	0.14	0.24
	30	0.10	0.20

Scattering parameters determined using transmission / Reflection method (waveguide and Vector Network Analyzer). Permittivity determined using Nicholson Ross Weir algorithm. Single measurement based values.

Additionally, ROHACELL® EC/EC-HT features all the exceptional thermomechanical properties and strength-to-weight ratios found in traditional ROHACELL® foam products. This combination of properties makes it an excellent sandwich core solution for components requiring both radar

absorption properties and superior mechanical performance.

Typical applications include use in stealth aircraft and electromagnetic shielding.

OUTSTANDING MECHANICAL PERFORMANCE

Due to its closed cell structure, ROHACELL® EC/EC-HT provides controlled resin absorption since the resin enters only the cut cells on the surface of the core material. This assures secure bonding of the core to the surface layers but adds no excessive resin weight to the finished part.

With excellent weight-specific mechanical properties at a very low weight, this lightweight foam is available in nominal densities starting at 75 kg/m³ (4.68 lb/ft³).

EFFICIENT PROCESSING

ROHACELL® EC/EC-HT can withstand the most demanding curing and processing conditions up to 180 °C (356 °F) and 7 bars depending on material density. It is compatible with all common curing processes including vacuum infusion, resin transfer molding, pre-preg autoclaving, as well as hand lay-up.

Notice: Evonik is aware of its product responsibility to the global community and takes reasonable care in the distribution of its products. ROHACELL® EC/EC-HT purchase and usage may require a license and proof of end user application. This product is: Subject to EU-Dual-Use-Verordnung VO (EU) 2021/821 – classification under: 1C101.

FOR MORE INFORMATION

If you have questions or would like to discuss using ROHACELL® EC/EC-HT in your application, we encourage you to talk with your local ROHACELL® representative.

Visit www.performance-foams.evonik.com to locate and directly connect with the contact in your region, by phone or email.

Property	Test Method*	Unit	ROHACELL® 71 EC	ROHACELL® 150 EC
Density	ISO 845 ASTM D 1622	kg/m ³ lbs/ft ³	75 (-) 4.68	150 (141) 9.36
Compressive Strength	ISO 844 ASTM D 1621	MPa psi	1.6 (-) 232	5.0 (3.9) 725
Tensile Strength	ISO 527-2 ASTM D 638	MPa psi	2.0 (-) 290	4.8 (-) 696
Tensile Modulus	ISO 527-2 ASTM D 638	MPa psi	105 (-) 15,200	245 (-) 35,500
Nom. Elongation at Break	ISO 527-2 ASTM D 638	%	3.2	N/A
Shear Strength	DIN 53294 ASTM C 273	MPa psi	1.0 (-) 145	3.5 (2.0) 508
Shear Modulus	DIN 53294 ASTM C 273	MPa psi	36 (-) 5,220	90 (87) 13,100
Coefficient of Thermal Expansion	ISO 11359-1/-2	1/K*10E-5	-	3.5
Compressive Creep Resistance ≤ 3.5 % for Non-HT Material	Temperature Pressure Time	°C MPa h	130 0.5 2	130 0.7 2
Compressive Creep Resistance ≤ 3.5 % for HT Material	Temperature Pressure Time	°C MPa h	180 0.5 2	180 0.7 2

Technical data values presented above are typical for nominal density, subject to normal manufacturing variations, and minimum values in (). *Data values are based on ISO & DIN standard test methods, however ASTM values can be confirmed upon request. All ROHACELL® products are closed-cell rigid foams based on polymethacrylimide (PMI) chemistry and contain no CFC's.

Disclaimer

ROHACELL® is a registered trademark of Evonik Industries and its subsidiaries.

This information and all technical and other advice are based on Evonik's present knowledge and experience. However, Evonik assumes no liability for such information or advice, including the extent to which such information or advice may relate to third party intellectual property rights. Evonik reserves the right to make any changes to information or advice at any time, without prior or subsequent notice. EVONIK DISCLAIMS ALL REPRESENTATIONS AND WARRANTIES, WHETHER EXPRESS OR IMPLIED, AND SHALL HAVE NO LIABILITY FOR, MERCHANTABILITY OF THE PRODUCT OR ITS FITNESS FOR A PARTICULAR PURPOSE (EVEN IF EVONIK IS AWARE OF SUCH PURPOSE), OR OTHERWISE. EVONIK SHALL NOT BE RESPONSIBLE FOR CONSEQUENTIAL, INDIRECT OR INCIDENTAL DAMAGES (INCLUDING LOSS OF PROFITS) OF ANY KIND. It is the customer's sole responsibility to arrange for inspection and testing of all products by qualified experts. Reference to trade names used by other companies is neither a recommendation, nor an endorsement of the corresponding product, and does not imply that similar products could not be used.

Evonik Operations GmbH

High Performance Polymers
Performance Foams
64293 Darmstadt, Germany
Phone +49 6151 18-1005

Evonik Corporation

Theodore, Alabama USA
Phone +1 866 764-6235

Evonik Specialty Chemicals (Shanghai) Co., Ltd.

Shanghai, China
Phone +86 21 6119 3788